

Manuscript Number: CSCM-D-14-00062R1

Title: ANKARA TEMPLE (MONUMENTUM ANCYRANUM) / RESTORATION FOR TEMPLE OF AUGUSTUS AND ROME

Article Type: Case Study

Keywords: Monumentum Ancyranum, Haci Bayram Mosque, Climatic Parameters, Petrographic Analysis, Restoration

Corresponding Author: Mr. can demirel,

Corresponding Author's Institution: kirkklareli university

First Author: Ahmet Gökdemir

Order of Authors: Ahmet Gökdemir; can demirel; Yavuz Yeğin; Zeynel Şimşek

Abstract: Temple of Augustus and Rome, also referred as Monumentum Ancyranum (Ankara Temple), is located near Haci Bayram Mosque in Ulus, Ankara. The temple which was built on behalf of Phrygian God `Men` in 2nd century BC has been destroyed. The temple whose remainings are present, on the other hand, was built for Roman Emperor `Augustus` (Gaius Octavius) in 25 BC in the name of a commitment sign by King Pilamenes, the son of King Amintos, of Galatia. . The places of 4 columns in the doorways and 2 columns in the rear sides are recognizable. In the current situation, only side walls and ornamented door part are remained. The original testament of Augustus in Temple of Rome, which is written in Latin and Greek and is telling the achievements of Augustus, is imitated in the mosque neighboring wall of Monumentum Ancyranum. Some parts of the patina is spilled because of the climatic parameters (wind, heat, precipitation, freeze). In result of the petrographic analysis made on the spilled parts of patina, it is concluded that the temple which has a great importance in the world history, has to be restored. By the result of the analyses (scanning electron microscope (SEM) analysis, EDS, X-Ray Diffraction (XRD) analysis), inner and outer sides of Naos are constructed without mortar. In the parts which are broken from the main body, calcium carbonate (CaCO₃) and magnesium carbonate (MgCO₃) are detected. Besides, it is observed that the main body of the temple is mainly consisted of calcium mineral. If that temple will be restored in the future, it is important to watch out calcium mineral property of the building.

Response to Reviewers: I did want to send the final version fixes

ANKARA TEMPLE (MONUMENTUM ANCYRANUM) / RESTORATION FOR TEMPLE OF AUGUSTUS AND ROME

Ahmet Gökdemir¹, Can Demirel^{2,*}, Yavuz Yeğin³, Zeynel Şimşek⁴

¹Gazi University, Faculty of Technology, Civil Engineering Department, 06500-Ankara.

^{2*}Kırklareli University, Pınarhisar Vocational High School, 39300-Kırklareli.

³Ardahan University, Faculty of Human Sciences and Humanities, 75000-Ardahan.

⁴Gazi University, Faculty of Arts, Department of Archaeology, 06500 Beşevler-Ankara.

SUMMARY

Temple of Augustus and Rome, also referred as Monumentum Ancyranum (Ankara Temple), is located near Hacı Bayram Mosque in Ulus, Ankara. The temple which was built on behalf of Phrygian God `Men` in 2nd century BC has been destroyed. The temple whose remainings are present, on the other hand, was built for Roman Emperor `Augustus` (Gaius Octavius) in 25 BC in the name of a commitment sign by King Pilamenes, the son of King Amintos, of Galatia. . The places of 4 columns in the doorways and 2 columns in the rear sides are recognizable. In the current situation, only side walls and ornamented door part are remained. The original testament of Augustus in Temple of Rome, which is written in Latin and Greek and is telling the achievements of Augustus, is imitated in the mosque neighboring wall of Monumentum Ancyranum. Some parts of the patina is spilled because of the climatic parameters (wind, heat, precipitation, freeze). In result of the petrographic analysis made on the spilled parts of patina, it is concluded that the temple which has a great importance in the world history, has to be restored. By the result of the analyses (scanning electron microscope (SEM) analysis, EDS, X-Ray Diffraction (XRD) analysis), inner and outer sides of Naos are constructed without mortar. In the parts which are broken from the main body, calcium carbonate (CaCO₃) and magnesium carbonate (MgCO₃) are detected. Besides, it is observed that the main body of the temple is mainly consisted of calcium mineral. If that temple will be restored in the future, it is important to watch out calcium mineral property of the building.

Keywords: Monumentum Ancyranum, Hacı Bayram Mosque, Climatic Parameters, Petrographic Analysis, Restoration

1. INTRODUCTION

The temple of Augustus and Rome in Ankara, is located a walking distance away from the first Grand National Assembly of Turkey building (Museum of Independence War) that founder of the Turkish Republic, Mustafa Kemal Atatürk and his companions has established, the temple is in the middle of the triangle of Anafartalar Avenue, Çankiri Avenue and Bent

deresi. The Haci Bayram-i Veli Mosque which was constructed by Islam Sufi and professor Haci Bayram Veli and his followers in 15th century, lies just nearby the temple. On 23 April 1920, before the inauguration of the first Grand National Assembly of Turkey, Mustafa Kemal Ataturk and the attendants prayed in Haci Bayram-I Veli Mosque. That hill where people made vow in history, is rushed by hundreds of local and foreigner visitors every day because of its spiritual energy.



Fig 1. The temple of Augustus and Rome, Ankara; Haci Bayram-i Veli Mosque [1].

The temple of Augustus and Rome was built as a temple in the new administrative center, Ankara (Ancyra), after the Roman invasion in Galatia Region in 25 BC. The temple was dedicated to Emperor Augustus and the local goddess of the city, `Roma`. After the death of Augustus, Romans inscribed a memorial on the walls of the temple both in Latin and Greek with red colored letters. The memorial, *Res Gestae divi Augusti*, is known as `Ankara Memorial` in Turkish. The inscription is an imitation of the original copy which was written by Augustus himself and was inscribed on 2 bronze columns in his mausoleum in the city of Rome. The mentioned original copy was destroyed centuries ago. The copy in Ankara Augustus Temple was preserved until now. The inscription is one of the most important documents of Roman period and it does not only present the achievements and accomplishments of Augustus, but also describes the institutional change, *res publica*, in the empire.

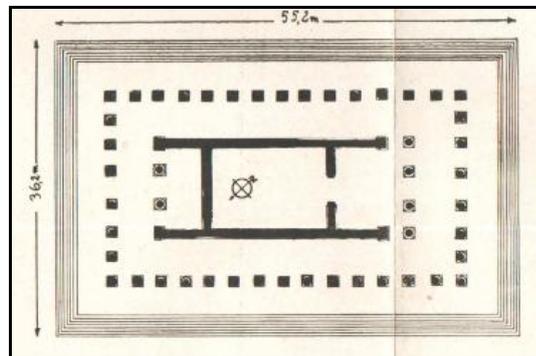
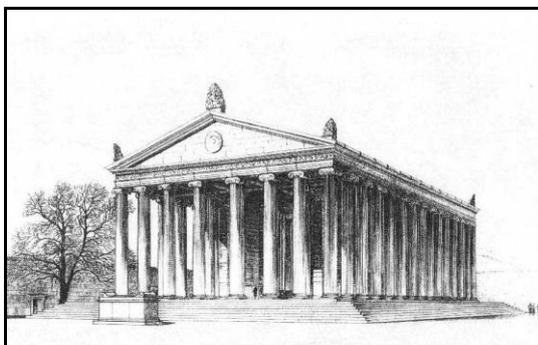


Fig 2. The temple in Ankara (Der Tempel in Ankara), [2].

Temple of Augustus in Ankara was designed in Corinth order, its dimensions are 36 x 54.82 m, it has a *pseudo-dipteral* plan and it was placed on a platform which is 2 meters high. In the beginnings of 6th century, Temple of Rome was converted to a church. In the middle of 15th century, before the death of Haci Bayram-i Veli, Haci Bayram Mosque was constructed, one side of whom is leaning against the temple. Having undergone changes over time, the mosque and tomb located right next to it are still capital's most important places of worship.

The Temple of Augustus, which is in the focus of interest of whole world, was first introduced to the academic society by Busbeck. Busbeck was in the peace committee that Emperor I. Ferdinand sent to Kanuni Sultan Suleyman in 1553-1555. Another attendant in the same committee, Dernchwan, described the temple as theater and palace in his journal. In 1670, in the time of Laisne, who was sent by the French government to purchase Greek manuscript, the temple was defined as Dervish convent. Tournefort, who arrived Ankara in 1701, drew the plan of the building and he thought that the building was a residence. Poul Lucas was the first traveller who realized that the Temple of Augustus was a temple in classical order in 1705. In 1735, a British, Pococke, took measurements of the temple and he identified that this place was the Temple of Augustus. In 1835, Texier, draw the temple with the mosque and the residences nearby. In 1836, during his visit to Ankara, Hamilton agreed with the landowners and copied the whole building. In 1861, Guillaume made the building survey of the temple. In 1865, historian and philologist Mommsen published the transcript of “*Res Gestae Divi Augusti*”. In 1882, manuscripts were studied again under the leadership of Humann. Kranker-Schede made the first archeological excavations in and around the temple in 1926-1928.

After the foundation of the Turkish Republic, first archeologists of the young Republic started to make scientific researches on that unique temple in the heart of Ankara. Between the years 1936-1938, all architectural designations of the temple was introduced by the researches under the leadership of Dr. Hamit Zubeyir Kosay. The elevation of temple is lower than today`s pavement level because of the modern formation of the area. The columns of the temple which are surrounding the courtyard are slightly visible. After the archeological and restoration studies of 1930, the work was stopped in that area for a long time period.

Considering the importance of the Temple of Augustus, World Monuments Watch declared the temple in world`s heritage list. In October 2001, it was listed as one of the hundred monuments which had to be rescued. The area and the surroundings of the Temple of Augustus in Ankara, which has a history of 2700 years, have been conserved by the directorate of Kültür ve Turizm Bakanlığı Kültür Varlıkları ve Müzeler Genel Müdürlüğü without harming its aesthetical properties.

It is necessary to work on conservation excavations, landscaping arrangements, restoration and conservation studies to determine the urgent actions to preserve the Temple of Augustus. By the fund provided by DOSIM Directorate, archeological excavation studies were executed between 15 September 2008/ 24 December 2008. The purpose of these excavations was cleaning and displaying the areas which were excavated in 1930, interpreting the old data with the newly discovered archeological data, analyzing the static structure of the soil that walls of the temple sit, detecting problems of wall binding properties and problems with checking of archeological stratigraphy and radiographic scanning in that highly elevated area of Ulus. On the other hand, for the first time in Turkish museology history Museum of Anatolian Civilizations broke grounds with Temple of Augustus excavations. The studies in and around the temple were published the daily in Museum of Anatolian Civilizations webpage. Thus, the data was shared with public and science world [1,3].

The Temple of Augustus and Rome is one of the most important and prioritized historical monuments of Turkey which has the urgent need of restoration. The details can be seen in the pictures below (Figure 3-9) [4].



Fig 3. Hac1 Bayram-ı Veli Turbeh



Fig 4. Temple of Augustus and Roma

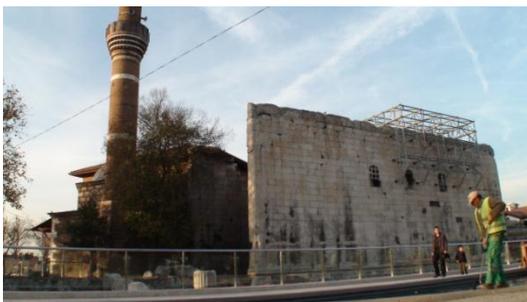


Fig 5. Temple of Augustus and Roma



Fig 6. Pool with Fountain



Fig 7. Deteriorations (External Walls)



Fig 8. Menderes Motif on the Exterior Walls



Fig 9. Deteriorations and Wrecks on the northern side walls

2. PREVIOUS STUDIES

2.1. Studies Related to the Temple of Augustus and Rome

Within the project named, Conservation Project of Temple of Augustus in Ankara, **Özen and Zararsız** (2009) made analysis researches. In the first phase, element analysis of two different deterioration products (black and yellow skin) were analyzed with portable non-destructive XRF machine. In the second phase, the same analysis has been made for the manuscript paint which was under serious danger of disintegration. The comparison between the spectrum of painted and unpainted parts indicated that the main difference between the two different parts was that the painted part was more ferrous. That result indicated that the red colored paint was composed of iron oxide. Besides the paint analysis, the same machine was used to compare the spectrums of yellow layered parts and the white layered parts. The calcium amounts for yellowed layered parts were seemed to be lower whereas the ferrous and lead amounts were higher. In addition, in the yellow layered parts, it is observed that calcium amount is double the black layered part. Thus it is concluded that yellow deterioration product is a protective layer against the atmospheric deteriorations [5].

Kadioğlu and his colleagues (2009) used GPR (Ground Penetrating Radar) method to investigate the presence of archeological remains in and around the temple. They also studied on the reasons of angular deflection of north side wall of the temple. They also researched the

presence of the remaining ferrous binding instruments which combines the structural units. For that purpose, they collected ground penetrating radar data in and around the temple and they collected profile data alongside the northern wall which is neighboring Haci Bayram Mosque. According to the collected data, they started excavation activities in the place called, Temple East 2, and they realized that the excavations results and GPR results match each other [6].

Sirt (2011) studied various techniques to evaluate the deterioration on the historical stone buildings by various microorganism species. In that sense, she studied on marble and andesite samples on Temple of Augustus. To measure the enzymatic activity, she used Fluorescein Diacetate (FDA) hydrolysis method which was used to determine microbial activity on soil. She realized that the dark stains were widely seen in the Temple of Augustus. That study proved that FDA hydrolysis, microflora and MPN methods are effective methods to evaluate biological deteriorations on the historical stones [7].

In 1997, **Botteri and Fangi** (2002) started their research on surveying and conservation activities in Monumentum Ancyranum under the project named, Trieste University Ancyra Project. That study includes the reports of interdisciplinary (history, archeology, photogrammetry, architecture) researches on Temple of Augustus which is the most important Roman temple standing in Ankara. In the leadership of P.Botteri, a lot of experts from different universities of Italy conducted that interdisciplinary study. The data which was obtained from the surveying studies was explained briefly. The tachometric and photogrammetric researches were done in two phases. The first phase was done until 1997 and it was restricted only with epigraphs. The second phase was done in 2000 and it covered the whole temple [8].

Wallace (2000), in his study, presented the manuscript which was carved with the painted colors on the wall of Temple of Augustus in Ankara. The author added an introduction, comments, grammar notes and keywords in his study. The text includes Roman Emperor Augustus` achievements, his activities, and his attempts to reach power. The Latin text was translated into English by the author [9].

In their study, **Caner and Böke** (1989), observed calcium oxalate on the original marble surfaces of Temple of Augustus which is located in a polluted area in Ankara. After the outer layer had been exfoliated, calcium oxalate was found on the new layer [10].

Caner and colleagues (1989a), investigated the effects of air pollution on the marbles of the Roman Temple of Augustus in Ankara. They examined samples taken from the exfoliations by x-ray powder diffraction, optical microscopy scanning electron, microscopy coupled to an edax system and limited chemical analysis. They described gypsum formation as a result of the study. They discussed deterioration in relation to Temple of Augustus. Atmospheric parameters and pollution data was evaluated. The building of a roof to protect against rain and snow was suggested as an immediate precaution [11].

3. MATERIAL AND METHOD

3.1. MATERIAL

Some parts of the patina were split from the interior and exterior surface of Naos because of the climatic parameters (wind, heat, precipitation, freeze). These were used as sample of the experiment.

3.1.1. The Preparation of Samples Which are Used in the Research [12]

All kinds of sample preparation process are done with modern equipment in Turkish Republic Ministry of Energy and Natural Resources, MTA Mineralogy and Petrography Analysis Laboratory Unit.

- The production of thin section and polished section for optic microscopic (petrographic analysis) analysis
- The production of polished thin section for fluid inclusion analysis
- Granulation of sample for XRD analysis
- Element microscopy, hot runner and polishing for organic petrography analysis
- The production of polished thin section for SEM, gold and carbon coating

Note: The above process and grinding process is carried out by turkey directorate general of mineral research and exploration samples (MTA). Sample sizes change according to the characteristics of the equipment in MTA.



Fig 10. Buehler analysis machine.

3.2. Method

Under the command of the administrator of Turkish Republic Ministry of Energy and Natural Resources, General Directorate of Mineral Research and Exploration, Mineralogical Researches Division, scanning electron microscope (SEM) and EDS, X-ray diffraction (XRD) analysis have been made meticulously.

3.2.1. Experimental Studies

Turkish Republic Ministry of Energy and Natural Resources, MTA Mineralogy and Petrography Analysis Laboratory is accredited according to TS EN ISO IEC 17025 standards. The experiments which were done according to ASTM standards in that study are explained step by step below.

3.2.1.1. Scanning Electron Microscope Analysis (SEM)

Scanning electron microscope is a technique which enables to produce high definition image with a focused beam of electrons. By the help of that technique, morphological, elemental and structural information can be gathered from low focusing to high focusing (x300.000 or more) [12].

Under high vacuum conditions, secondary electron (SE), back-scattered electrons (BSE) or mixed (SE+BSE) signal visions are gathered and photographed. In addition, nonstandard qualitative elemental analysis (SEM-EDS) is made on the inspected sample with X-ray mapping.

3.2.1.2. X-ray Diffraction (XRD Analysis)

XRD is a technique which is used to introduce small particle sized minerals according to their crystal structural properties if it is impossible to do that with optical microscopes. In that technique, the sample which will be analyzed, is grinded and is turned into powder form and it is analyzed with the XRD analysis instruments. XRD analysis which is made in the division, is done with the instruments Bruker D8 Advance, Panalytical X'Pert Powder and Philips PW 1830 [12].

In standard, qualitative XRD analysis, samples are analyzed with Ni filtered, X-ray tubed instruments under 2-70 °C. The produced X-ray diffractograms are evaluated according to ASTM- 295 standards.

With standard XRD analysis, enrichment process is applied for undefined clay typed minerals and qualitative XRD detailed clay analysis is made. In that method, after standard analysis process, the enriched samples are analyzed with Ni filtered Cu X-ray tubed instruments between 2-40°C as normal, with ethylene glycol, oven-dried (550°C). The obtained X-ray diffractograms are evaluated according to ASTM 295 standards. The quantitative rates of minerals (quantitative XRD analysis) are calculated by using Rietveld method. With the applied method, the necessary corrections of peak values (Rietveld Refinement) on the diffractograms which are obtained from high definition Pixel based detectors, are made by using the database of crystalline structure files. The percentage values of minerals are given with the rates of standard deviations.

3.2.2 Climatic Parameters Belonging to Ankara

Statistical Data belonging to Ankara between years 1960-2012 which is obtained from Turkish State Meteorological Service (Table 1) [13].

Table 1. The Data of Climatic Parameters Belonging to Ankara (1960-2012)

ANKARA	January	February	March	April	May	June	July	August	September	October	November	December
Average Temperature (°C)	0.3	1.8	6.1	11.3	16.1	20.2	23.5	23.3	18.7	13.1	7.1	2.7
Average Highest Temperature (°C)	4.3	6.4	11.7	17.2	22.2	26.6	30.2	30.2	26.0	19.9	12.8	6.6
Average Lowest Temperature (°C)	-3.0	-2.2	1.0	5.7	9.7	13.0	16.0	16.0	11.9	7.4	2.5	-0.6
Average Sun taking (Hours)	2.5	3.5	5.2	6.3	8.4	10.2	11.3	10.6	9.2	6.4	4.4	2.3
Average Rainy Days	11.7	11.0	10.9	12.0	12.5	8.6	3.8	2.8	3.8	7.1	8.6	11.8
Monthly Total Rainy Days (kg/m ²)	41.8	36.9	38.7	49.0	51.2	35.4	14.5	10.9	18.5	30.2	33.9	46.9
Highest Temperature (°C)	16.6	19.9	26.4	30.6	33.0	37.0	41.0	40.4	36.0	32.2	24.4	19.8
Lowest Temperature (°C)	-21.2	-21.5	-19.2	-6.7	-1.6	4.7	6.8	6.3	2.5	-3.4	-10.5	-17.2

Table 2. The Highest Values of the Climate Parameters of Ankara Province (1960-2012).

Daily Total Maximum Rain Amount	11.06.1997	88.9 kg/m ²	Daily Fastest Wind	12.01.1968	115.6 km/h	The Highest Snow	05.01.2002	30.0 cm
---------------------------------	------------	------------------------	--------------------	------------	------------	------------------	------------	---------

According to the information from the General Directorate of Meteorology, Republic of Turkey Ministry of Forestry and Water Affairs, the average lowest temperature in Ankara between years 1960-2012 is -21.5 °C and the highest is +41.0 °C, the average monthly total rainfall is 51.2 kg/m² (Table 1). In addition, the highest daily rainfall total is 88.9 kg/m² on 11.06.1997, the fastest wind is 115.6 km/h on 12.01.1968, the highest daily snow is 30.0 cm on 05.01.2002 (Table 2). Therefore, Naos's walls are under the influence of these climate parameters (temperature, wind, precipitation, freeze) for centuries. This situation causes freeze-thaw on the patina layer, as a result, the surface is eroded by spalling. Plus, wind, temperature difference and rainfall accelerate spillages from the layer of patina. Building

materials and chemicals to be used in the restoration of this historic sanctuary should be selected taking into account climatic parameters of the capital Ankara.

4. FINDINGS AND DISCUSSION

4.1. Scanning Electron Microscope Analysis (SEM) and EDS Findings

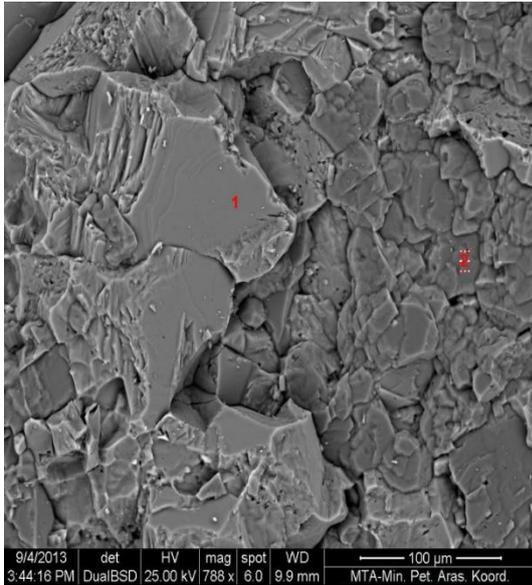


Fig 11. SEM Analysis (1,2) photograph

As seen in Figure 1, SEM analysis was performed and Energy Dispersive X-ray Spectroscopy (EDS) analysis was performed for the points 1 and 2. The results are shown in Figure 12 and Figure 13.

The photographs of scanning electron microscope SEM were taken with the scale 1 cm for 2 μm . It is taken with x300.000 and more zooming (Figure 11). The technique is used for taking high definition image with a focused beam of electrons. By the help of that technique, morphological, elemental and structural information can be gathered from low focusing to high focusing. Under high vacuum conditions, secondary electron (SE), back-scattered electrons (BSE) or mixed (SE+BSE) signal visions are gathered and photographed.

In the regions which include that structure, the particles are mostly arranged homogeneous, the shapes of them are cornered and fractured and the dimensions are in micrometers. The distances between these particles are seen to be narrowed. The dimensions are around 0.35-0.91 μm . In addition, spherical and closed spacing particles are seen along with geometrical shaped particles.

Another property which is seen in the SEM photographs is that the particles which have different sizes and shapes, have similar color tones. Although some particles are dark grey in color, in some regions light grey and white particles are also seen. That situation is obvious in all successive analysis. That image which is seen in the SEM photographs is a typical

crystalline structural shape which is also defined in literature. A homogenous structure is observed, the particles are observed to be in a tight form, large cavities and large particles are not observed.

In addition, nonstandard qualitative elemental analysis (SEM-EDS) is made on the inspected sample with X-ray mapping. (Figure 12 and Figure 13).

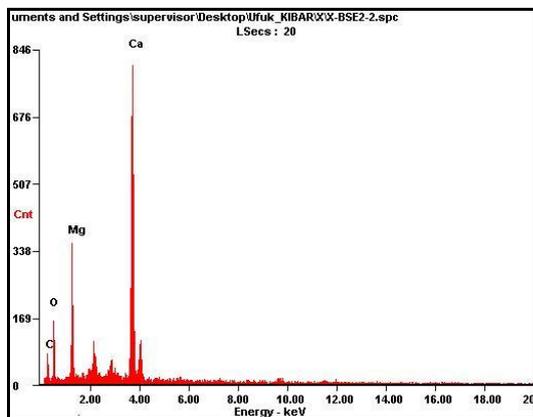


Fig 12 EDS Analysis Graphic

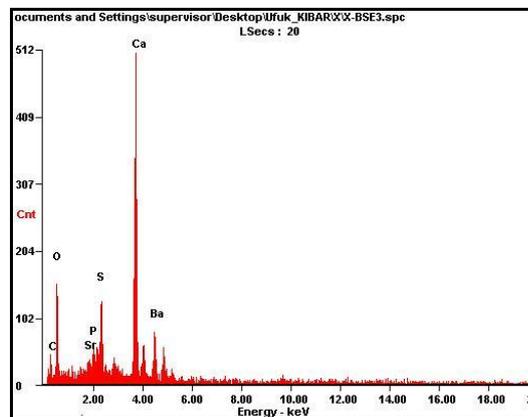


Fig 13 EDS Analysis Graphic

EDS analysis were applied by focusing on a point of 2 μm and it is applied by searching an area of (50 μm x 50 μm). That procedure is applied in a depth of 2.5 μm . In that analysis, the pure structure of the experiment sample is observed. In Table 3 and Table 4, atomic percentages which were obtained from EDS analysis are given.

Table 3 EDS atomic percentages

Elements	Atomic Percentage
C	29.86
O	40.37
Mg	12.80
Ca	16.96
Total	100.00

Table 4 EDS and atomic percentages

Elements	Atomic Percentage
C	24.47
O	52.27
Sr	0.67
P	1.73
S	4.08
Ca	14.00
Ba	2.79
Total	100.00

Moreover, EDS analysis indicate that various dissolutions were not formed, thus mainly a pure structure is observed during the analysis.

4.2. X-ray Diffraction (XRD Analysis) Findings

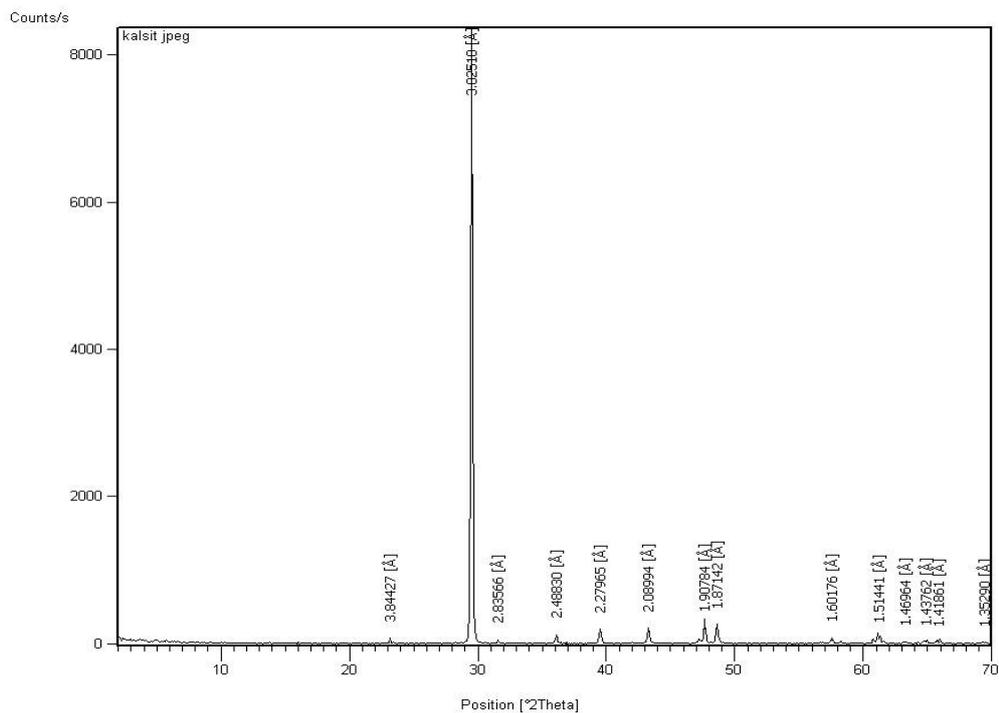


Fig 14.XRD Analysis Graphic

According to the results of XRD analysis in the Figure 14, the exterior and interior of main body of Naos are composed of calcite mineral.

While defining the microstructure of the experiment sample and while examining the crystal structure, X-ray analysis provided important findings. In the process, applying sintering with heat, the experiment samples are monitored from the nucleation phase to the last crystallization phase for crystallization duration and structural changes with XRD. These analysis have lots of benefits for observing different crystalline structures and for defining the appropriate heating conditions as well. Because of the same reason, the similarity between peak points indicates that the structure, which constitutes the sample, is in a pure phase, meaning that it is mainly composed of calcite mineral.

That situation is observed clearly in SEM photographs and it is compatible with XRD results.

5. RESULTS AND SUGGESTIONS

According to the data obtained from Turkish State Meteorological Service, the average temperature in Ankara is, lowest; $-21.5\text{ }^{\circ}\text{C}$ and highest; $+41.0\text{ }^{\circ}\text{C}$. Average of monly total rate amount is 51.2 kg/m^2 (Table 1). In addition, the daily total maximum rain amount is 88.9 kg/m^2 on 11.06.1997. Daily fastest wind is 115.6 km/hr on 12.01.1968. Daily highest snow amount is 30.0 cm in 05.01.2002 (Table 2). Therefore, the walls of Naos are under these climatic parameters (wind, heat, precipitation, freeze) for hundreds of years. That condition leads to freeze and thaw in patina layer and that causes spilling in the surface. Moreover; wind, temperature differences and rains accelerate the breaking of pieces from patina layer. The construction materials and construction chemicals which will be used for restoration of that historical temple have to be chosen with respect to the climatic parameters of Ankara.

Turkish Republic Ministry of Energy and Natural Resources, MTA Mineralogy and Petrography Analysis Laboratory Unit has made Scanning Electron Microscope (SEM) and EDS (Figure 11,12,13), X-ray Diffraction (XRD) analysis (Figure 14) . With respect to the analysis, the main component of the temple is determined to be stone with calcite mineral. According to that determination, the materials and chemicals which will be used in the restoration process, have to have calcite mineral origins or they have to be compatible with calcite mineral.

The pool with fountain (Figure 6), on the south side of the historical temple, is increasing the moisture rate and it is accelerating the deterioration of the Greek manuscript on the suth side wall of the temple. The original copy of manuscript was in Rome and it was destructed centuries ago. Therefore it is very important to keep the only remaining copy. The information given in the manuscript do not only belong to Roman Emperor Augustus, but also include important information about Roman history. Therefore, rather than a fountain, a classical hydrophore (pressurized recirculation pump) where the water is pouring step by step can be used. A pool system where the water is recirculating by machines can be considered.

A solution for roofing, which is compatible with the roofing system in the original building (Figure 2), can preserve the structure against climatic parameters and it can provide sustainability for the static equilibrium of the building. Such a precaution has to be taken urgently.

The temple whose importance for world heritage is unquestionable, has to be restored faithful to its originality. Environmental formation of the temple has to be in accordance with the surrounding structures. The historical structure has to be accessible to humanity as a museum, thus the honor, it deserves in the history, will be given back to it.

REFERENCES

1. Yurttagül, E., ‘‘Augustus Tapınađı Sondaj, Kurtarma Kazısı, Çevre Düzenlemesi ve Temizlik Çalışmaları’’, T.C. Ankara Valiliđi İl Kültür ve Turizm Müdürlüğü Anadolu Medeniyetleri Müzesi Müdürlüğü, Ankara, (2008).
2. M, Schede., D, Krencker., ‘‘*Der Tempel in Ankara*’’, pp. 43-44, Berlin - Leipzig, (1936).
3. Dođan, C, ‘‘Çevre Sorunlarının Tespitinde Ortaya Çıkan Kirliliklerin Mahalli İdarelerce Temizlenmesi; İlgili Hareket Alanını Belirleyen Normatif Pozitif Hukuk Kuralları’’, Askerî Yüksek İdâre Mahkemesi Dergisi, Sayı:19, s. 211, Ankara, (2004).
4. Aslan, İ., Güler, Ç., Yumak, E., ‘‘Ankara Augustus ve Roma Mabedi Fotoğraf Albümü’’, Ankara, (2013).
5. Özen, L., Zararsız, A., ‘‘Anadolu Medeniyetleri Müzesi Konservasyon Laboratuvarı Araştırma Çalışmaları’’, T.C. Ankara Valiliđi İl Kültür ve Turizm Müdürlüğü Anadolu Medeniyetleri Müzesi Müdürlüğü 2007-2008 Yıllığı, Ayrı Basım Sayı: XXI, S:309 Ankara, (2009).
6. Kadiođlu, S., Kadiođlu, K., Y., Akyol, A., A., ‘‘Augustus Tapınađı Arkeometrik İncelemeleri Kapsamında Jeofizik Çalışmalar’’, T.C. Kültür ve Turizm Bakanlığı Kültür Varlıkları ve Müzeler Genel Müdürlüğü 31. Uluslararası Kazı, Araştırma ve Arkeometri Sempozyumu, 25. Arkeometri Sonuçları Toplantısı, T.C. Kültür ve Turizm Bakanlığı Yayın No: 3251 / Kültür Varlıkları ve Müzeler Genel Müdürlüğü Yayın No: 144, s. 431-440, Denizli, Türkiye, 25-29 Mayıs (2009).
7. Sirt, E., ‘‘ Evaluation of biodeterioration in Nemrut Mount Monument and Temple of Augustus by using various techniques’’, METU, Ankara, (2011).
8. Botteri, P., Fangi G., ‘‘The Ancyra Project: the Temple of Augustus and Rome in Ankara -UNESCO 30th Anniversary Virtual Congress’’, 21-23, October, Alexandria, (2002).
9. Wallace, R., (Ed.) ‘‘Res gestae divi Augusti: as recorded in the **Monumentum Ancyranum** and the **Monumentum antiochenum**: introduction, grammatical notes, historical commentary, facing vocabulary’’, Wauconda, Ill, Bolchazy-Carducci Publishers, (2000).
10. Caner, E., N., Böke, H., ‘‘Occurrence of Calcium Oxalates on Marble Monuments in Anatolia’’, Proceedings of International Symposium on : The Oxalate Films: Origin and Significance in the Conservation of Works of Art, G. Alessandrini Ed., Centro CNR ‘‘GINO BOZZA’’ pp.299-307; Milano, (1989).
11. Caner, E., N., Göktürk, H., Türkmenođlu, A., G., Eseller, G., ‘‘Effects of Air Pollution on the Monuments in Ankara, Case Study: Temple of Augustus’’, Durability of Building Materials, 5, pp:463-473, (1989a).
12. Maden Tetkik Arama Genel Müdürlüğü, Petrografi Laboratuvarı, Ankara, (2013).
13. http://www.mgm.gov.tr/App Themes/mavimavi/site_baslik_v1_tr.png, (2013).

ANKARA TEMPLE (MONUMENTUM ANCYRANUM) / RESTORATION FOR TEMPLE OF AUGUSTUS AND ROME

Ahmet Gökdemir¹, Can Demirel^{2,*}, Yavuz Yeğin³, Zeynel Şimşek⁴

¹Gazi University, Faculty of Technology, Civil Engineering Department, 06500-Ankara.

^{2*}Kırklareli University, Pınarhisar Vocational High School, 39300-Kırklareli.

³Ardahan University, Faculty of Human Sciences and Humanities, 75000-Ardahan.

⁴Gazi University, Faculty of Arts, Department of Archaeology, 06500 Beşevler-Ankara.

SUMMARY

Temple of Augustus and Rome, also referred as Monumentum Ancyranum (Ankara Temple), is located near Hacı Bayram Mosque in Ulus, Ankara. The temple which was built on behalf of Phrygian God `Men` in 2nd century BC has been destroyed. The temple whose remainings are present, on the other hand, was built for Roman Emperor `Augustus` (Gaius Octavius) in 25 BC in the name of a commitment sign by King Pilamenes, the son of King Amintos, of Galatia. . The places of 4 columns in the doorways and 2 columns in the rear sides are recognizable. In the current situation, only side walls and ornamented door part are remained. The original testament of Augustus in Temple of Rome, which is written in Latin and Greek and is telling the achievements of Augustus, is imitated in the mosque neighboring wall of Monumentum Ancyranum. Some parts of the patina is spilled because of the climatic parameters (wind, heat, precipitation, freeze). In result of the petrographic analysis made on the spilled parts of patina, it is concluded that the temple which has a great importance in the world history, has to be restored. By the result of the analyses (scanning electron microscope (SEM) analysis, EDS, X-Ray Diffraction (XRD) analysis), inner and outer sides of Naos are constructed without mortar. In the parts which are broken from the main body, calcium carbonate (CaCO₃) and magnesium carbonate (MgCO₃) are detected. Besides, it is observed that the main body of the temple is mainly consisted of calcium mineral. If that temple will be restored in the future, it is important to watch out calcium mineral property of the building.

Keywords: Monumentum Ancyranum, Hacı Bayram Mosque, Climatic Parameters, Petrographic Analysis, Restoration

1. INTRODUCTION

The temple of Augustus and Rome in Ankara, is located a walking distance away from the first Grand National Assembly of Turkey building (Museum of Independence War) that founder of the Turkish Republic, Mustafa Kemal Atatürk and his companions has established, the temple is in the middle of the triangle of Anafartalar Avenue, Çankiri Avenue and Bent

deresi. The Haci Bayram-i Veli Mosque which was constructed by Islam Sufi and professor Haci Bayram Veli and his followers in 15th century, lies just nearby the temple. On 23 April 1920, before the inauguration of the first Grand National Assembly of Turkey, Mustafa Kemal Ataturk and the attendants prayed in Haci Bayram-I Veli Mosque. That hill where people made vow in history, is rushed by hundreds of local and foreigner visitors every day because of its spiritual energy.



Fig 1. The temple of Augustus and Rome, Ankara; Haci Bayram-i Veli Mosque [1].

The temple of Augustus and Rome was built as a temple in the new administrative center, Ankara (Ancyra), after the Roman invasion in Galatia Region in 25 BC. The temple was dedicated to Emperor Augustus and the local goddess of the city, `Roma`. After the death of Augustus, Romans inscribed a memorial on the walls of the temple both in Latin and Greek with red colored letters. The memorial, *Res Gestae divi Augusti*, is known as `Ankara Memorial` in Turkish. The inscription is an imitation of the original copy which was written by Augustus himself and was inscribed on 2 bronze columns in his mausoleum in the city of Rome. The mentioned original copy was destroyed centuries ago. The copy in Ankara Augustus Temple was preserved until now. The inscription is one of the most important documents of Roman period and it does not only present the achievements and accomplishments of Augustus, but also describes the institutional change, *res publica*, in the empire.

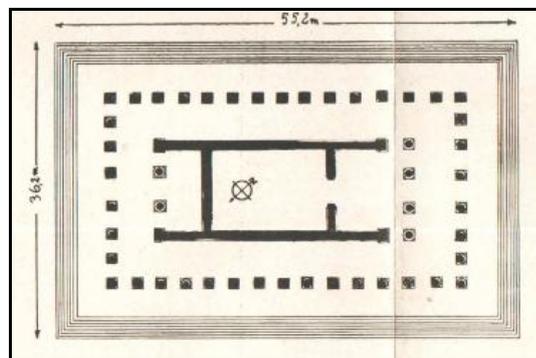
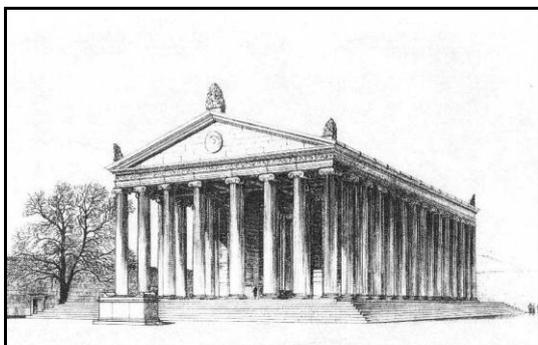


Fig 2. The temple in Ankara (Der Tempel in Ankara), [2].

Temple of Augustus in Ankara was designed in Corinth order, its dimensions are 36 x 54.82 m, it has a *pseudo-dipteral* plan and it was placed on a platform which is 2 meters high. In the beginnings of 6th century, Temple of Rome was converted to a church. In the middle of 15th century, before the death of Haci Bayram-i Veli, Haci Bayram Mosque was constructed, one side of whom is leaning against the temple. Having undergone changes over time, the mosque and tomb located right next to it are still capital's most important places of worship.

The Temple of Augustus, which is in the focus of interest of whole world, was first introduced to the academic society by Busbeck. Busbeck was in the peace committee that Emperor I. Ferdinand sent to Kanuni Sultan Suleyman in 1553-1555. Another attendant in the same committee, Dernchwan, described the temple as theater and palace in his journal. In 1670, in the time of Laisne, who was sent by the French government to purchase Greek manuscript, the temple was defined as Dervish convent. Tournefort, who arrived Ankara in 1701, drew the plan of the building and he thought that the building was a residence. Poul Lucas was the first traveller who realized that the Temple of Augustus was a temple in classical order in 1705. In 1735, a British, Pococke, took measurements of the temple and he identified that this place was the Temple of Augustus. In 1835, Texier, draw the temple with the mosque and the residences nearby. In 1836, during his visit to Ankara, Hamilton agreed with the landowners and copied the whole building. In 1861, Guillaume made the building survey of the temple. In 1865, historian and philologist Mommsen published the transcript of “*Res Gestae Divi Augusti*”. In 1882, manuscripts were studied again under the leadership of Humann. Kranker-Schede made the first archeological excavations in and around the temple in 1926-1928.

After the foundation of the Turkish Republic, first archeologists of the young Republic started to make scientific researches on that unique temple in the heart of Ankara. Between the years 1936-1938, all architectural designations of the temple was introduced by the researches under the leadership of Dr. Hamit Zubeyir Kosay. The elevation of temple is lower than today`s pavement level because of the modern formation of the area. The columns of the temple which are surrounding the courtyard are slightly visible. After the archeological and restoration studies of 1930, the work was stopped in that area for a long time period.

Considering the importance of the Temple of Augustus, World Monuments Watch declared the temple in world`s heritage list. In October 2001, it was listed as one of the hundred monuments which had to be rescued. The area and the surroundings of the Temple of Augustus in Ankara, which has a history of 2700 years, have been conserved by the directorate of Kültür ve Turizm Bakanlığı Kültür Varlıkları ve Müzeler Genel Müdürlüğü without harming its aesthetical properties.

It is necessary to work on conservation excavations, landscaping arrangements, restoration and conservation studies to determine the urgent actions to preserve the Temple of Augustus. By the fund provided by DOSIM Directorate, archeological excavation studies were executed between 15 September 2008/ 24 December 2008. The purpose of these excavations was cleaning and displaying the areas which were excavated in 1930, interpreting the old data with the newly discovered archeological data, analyzing the static structure of the soil that walls of the temple sit, detecting problems of wall binding properties and problems with checking of archeological stratigraphy and radiographic scanning in that highly elevated area of Ulus. On the other hand, for the first time in Turkish museology history Museum of Anatolian Civilizations broke grounds with Temple of Augustus excavations. The studies in and around the temple were published the daily in Museum of Anatolian Civilizations webpage. Thus, the data was shared with public and science world [1,3].

The Temple of Augustus and Rome is one of the most important and prioritized historical monuments of Turkey which has the urgent need of restoration. The details can be seen in the pictures below (Figure 3-9) [4].



Fig 3. Hac1 Bayram-ı Veli Turbeh



Fig 4. Temple of Augustus and Roma

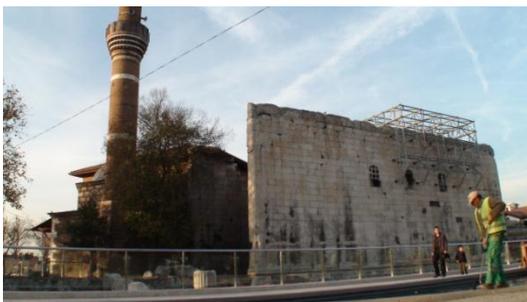


Fig 5. Temple of Augustus and Roma



Fig 6. Pool with Fountain



Fig 7. Deteriorations (External Walls)



Fig 8. Menderes Motif on the Exterior Walls



Fig 9. Deteriorations and Wrecks on the northern side walls

2. PREVIOUS STUDIES

2.1. Studies Related to the Temple of Augustus and Rome

Within the project named, Conservation Project of Temple of Augustus in Ankara, **Özen and Zararsız** (2009) made analysis researches. In the first phase, element analysis of two different deterioration products (black and yellow skin) were analyzed with portable non-destructive XRF machine. In the second phase, the same analysis has been made for the manuscript paint which was under serious danger of disintegration. The comparison between the spectrum of painted and unpainted parts indicated that the main difference between the two different parts was that the painted part was more ferrous. That result indicated that the red colored paint was composed of iron oxide. Besides the paint analysis, the same machine was used to compare the spectrums of yellow layered parts and the white layered parts. The calcium amounts for yellowed layered parts were seemed to be lower whereas the ferrous and lead amounts were higher. In addition, in the yellow layered parts, it is observed that calcium amount is double the black layered part. Thus it is concluded that yellow deterioration product is a protective layer against the atmospheric deteriorations [5].

Kadioğlu and his colleagues (2009) used GPR (Ground Penetrating Radar) method to investigate the presence of archeological remains in and around the temple. They also studied on the reasons of angular deflection of north side wall of the temple. They also researched the

presence of the remaining ferrous binding instruments which combines the structural units. For that purpose, they collected ground penetrating radar data in and around the temple and they collected profile data alongside the northern wall which is neighboring Haci Bayram Mosque. According to the collected data, they started excavation activities in the place called, Temple East 2, and they realized that the excavations results and GPR results match each other [6].

Sirt (2011) studied various techniques to evaluate the deterioration on the historical stone buildings by various microorganism species. In that sense, she studied on marble and andesite samples on Temple of Augustus. To measure the enzymatic activity, she used Fluorescein Diacetate (FDA) hydrolysis method which was used to determine microbial activity on soil. She realized that the dark stains were widely seen in the Temple of Augustus. That study proved that FDA hydrolysis, microflora and MPN methods are effective methods to evaluate biological deteriorations on the historical stones [7].

In 1997, **Botteri and Fangi** (2002) started their research on surveying and conservation activities in Monumentum Ancyranum under the project named, Trieste University Ancyra Project. That study includes the reports of interdisciplinary (history, archeology, photogrammetry, architecture) researches on Temple of Augustus which is the most important Roman temple standing in Ankara. In the leadership of P.Botteri, a lot of experts from different universities of Italy conducted that interdisciplinary study. The data which was obtained from the surveying studies was explained briefly. The tachometric and photogrammetric researches were done in two phases. The first phase was done until 1997 and it was restricted only with epigraphs. The second phase was done in 2000 and it covered the whole temple [8].

Wallace (2000), in his study, presented the manuscript which was carved with the painted colors on the wall of Temple of Augustus in Ankara. The author added an introduction, comments, grammar notes and keywords in his study. The text includes Roman Emperor Augustus` achievements, his activities, and his attempts to reach power. The Latin text was translated into English by the author [9].

In their study, **Caner and Böke** (1989), observed calcium oxalate on the original marble surfaces of Temple of Augustus which is located in a polluted area in Ankara. After the outer layer had been exfoliated, calcium oxalate was found on the new layer [10].

Caner and colleagues (1989a), investigated the effects of air pollution on the marbles of the Roman Temple of Augustus in Ankara. They examined samples taken from the exfoliations by x-ray powder diffraction, optical microscopy scanning electron, microscopy coupled to an edax system and limited chemical analysis. They described gypsum formation as a result of the study. They discussed deterioration in relation to Temple of Augustus. Atmospheric parameters and pollution data was evaluated. The building of a roof to protect against rain and snow was suggested as an immediate precaution [11].

3. MATERIAL AND METHOD

3.1. MATERIAL

Some parts of the patina were split from the interior and exterior surface of Naos because of the climatic parameters (wind, heat, precipitation, freeze). These were used as sample of the experiment.

3.1.1. The Preparation of Samples Which are Used in the Research [12]

All kinds of sample preparation process are done with modern equipment in Turkish Republic Ministry of Energy and Natural Resources, MTA Mineralogy and Petrography Analysis Laboratory Unit.

- The production of thin section and polished section for optic microscopic (petrographic analysis) analysis
- The production of polished thin section for fluid inclusion analysis
- Granulation of sample for XRD analysis
- Element microscopy, hot runner and polishing for organic petrography analysis
- The production of polished thin section for SEM, gold and carbon coating

Note: The above process and grinding process is carried out by turkey directorate general of mineral research and exploration samples (MTA). Sample sizes change according to the characteristics of the equipment in MTA.



Fig 10. Buehler analysis machine.

3.2. Method

Under the command of the administrator of Turkish Republic Ministry of Energy and Natural Resources, General Directorate of Mineral Research and Exploration, Mineralogical Researches Division, scanning electron microscope (SEM) and EDS, X-ray diffraction (XRD) analysis have been made meticulously.

3.2.1. Experimental Studies

Turkish Republic Ministry of Energy and Natural Resources, MTA Mineralogy and Petrography Analysis Laboratory is accredited according to TS EN ISO IEC 17025 standards. The experiments which were done according to ASTM standards in that study are explained step by step below.

3.2.1.1. Scanning Electron Microscope Analysis (SEM)

Scanning electron microscope is a technique which enables to produce high definition image with a focused beam of electrons. By the help of that technique, morphological, elemental and structural information can be gathered from low focusing to high focusing (x300.000 or more) [12].

Under high vacuum conditions, secondary electron (SE), back-scattered electrons (BSE) or mixed (SE+BSE) signal visions are gathered and photographed. In addition, nonstandard qualitative elemental analysis (SEM-EDS) is made on the inspected sample with X-ray mapping.

3.2.1.2. X-ray Diffraction (XRD Analysis)

XRD is a technique which is used to introduce small particle sized minerals according to their crystal structural properties if it is impossible to do that with optical microscopes. In that technique, the sample which will be analyzed, is grinded and is turned into powder form and it is analyzed with the XRD analysis instruments. XRD analysis which is made in the division, is done with the instruments Bruker D8 Advance, Panalytical X'Pert Powder and Philips PW 1830 [12].

In standard, qualitative XRD analysis, samples are analyzed with Ni filtered, X-ray tubed instruments under 2-70 °C. The produced X-ray diffractograms are evaluated according to ASTM- 295 standards.

With standard XRD analysis, enrichment process is applied for undefined clay typed minerals and qualitative XRD detailed clay analysis is made. In that method, after standard analysis process, the enriched samples are analyzed with Ni filtered Cu X-ray tubed instruments between 2-40°C as normal, with ethylene glycol, oven-dried (550°C). The obtained X-ray diffractograms are evaluated according to ASTM 295 standards. The quantitative rates of minerals (quantitative XRD analysis) are calculated by using Rietveld method. With the applied method, the necessary corrections of peak values (Rietveld Refinement) on the diffractograms which are obtained from high definition Pixel based detectors, are made by using the database of crystalline structure files. The percentage values of minerals are given with the rates of standard deviations.

3.2.2 Climatic Parameters Belonging to Ankara

Statistical Data belonging to Ankara between years 1960-2012 which is obtained from Turkish State Meteorological Service (Table 1) [13].

Table 1. The Data of Climatic Parameters Belonging to Ankara (1960-2012)

ANKARA	January	February	March	April	May	June	July	August	September	October	November	December
Average Temperature (°C)	0.3	1.8	6.1	11.3	16.1	20.2	23.5	23.3	18.7	13.1	7.1	2.7
Average Highest Temperature (°C)	4.3	6.4	11.7	17.2	22.2	26.6	30.2	30.2	26.0	19.9	12.8	6.6
Average Lowest Temperature (°C)	-3.0	-2.2	1.0	5.7	9.7	13.0	16.0	16.0	11.9	7.4	2.5	-0.6
Average Sun taking (Hours)	2.5	3.5	5.2	6.3	8.4	10.2	11.3	10.6	9.2	6.4	4.4	2.3
Average Rainy Days	11.7	11.0	10.9	12.0	12.5	8.6	3.8	2.8	3.8	7.1	8.6	11.8
Monthly Total Rainy Days (kg/m ²)	41.8	36.9	38.7	49.0	51.2	35.4	14.5	10.9	18.5	30.2	33.9	46.9
Highest Temperature (°C)	16.6	19.9	26.4	30.6	33.0	37.0	41.0	40.4	36.0	32.2	24.4	19.8
Lowest Temperature (°C)	-21.2	-21.5	-19.2	-6.7	-1.6	4.7	6.8	6.3	2.5	-3.4	-10.5	-17.2

Table 2. The Highest Values of the Climate Parameters of Ankara Province (1960-2012).

Daily Total Maximum Rain Amount	11.06.1997	88.9 kg/m ²	Daily Fastest Wind	12.01.1968	115.6 km/h	The Highest Snow	05.01.2002	30.0 cm
---------------------------------	------------	------------------------	--------------------	------------	------------	------------------	------------	---------

According to the information from the General Directorate of Meteorology, Republic of Turkey Ministry of Forestry and Water Affairs, the average lowest temperature in Ankara between years 1960-2012 is -21.5 °C and the highest is +41.0 °C, the average monthly total rainfall is 51.2 kg/m² (Table 1). In addition, the highest daily rainfall total is 88.9 kg/m² on 11.06.1997, the fastest wind is 115.6 km/h on 12.01.1968, the highest daily snow is 30.0 cm on 05.01.2002 (Table 2). Therefore, Naos's walls are under the influence of these climate parameters (temperature, wind, precipitation, freeze) for centuries. This situation causes freeze-thaw on the patina layer, as a result, the surface is eroded by spalling. Plus, wind, temperature difference and rainfall accelerate spillages from the layer of patina. Building

materials and chemicals to be used in the restoration of this historic sanctuary should be selected taking into account climatic parameters of the capital Ankara.

4. FINDINGS AND DISCUSSION

4.1. Scanning Electron Microscope Analysis (SEM) and EDS Findings

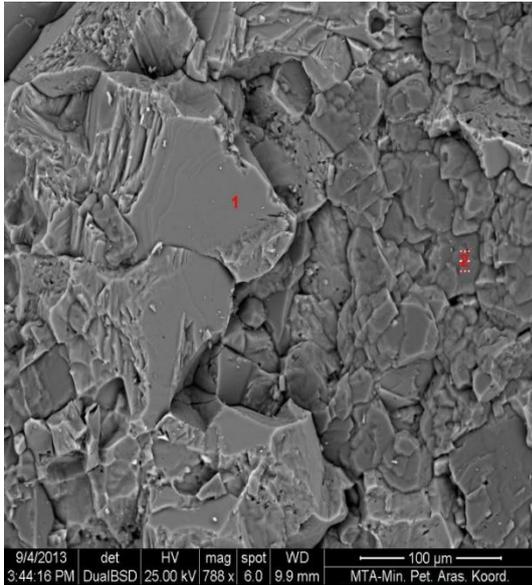


Fig 11. SEM Analysis (1,2) photograph

As seen in Figure 1, SEM analysis was performed and Energy Dispersive X-ray Spectroscopy (EDS) analysis was performed for the points 1 and 2. The results are shown in Figure 12 and Figure 13.

The photographs of scanning electron microscope SEM were taken with the scale 1 cm for 2 μm . It is taken with x300.000 and more zooming (Figure 11). The technique is used for taking high definition image with a focused beam of electrons. By the help of that technique, morphological, elemental and structural information can be gathered from low focusing to high focusing. Under high vacuum conditions, secondary electron (SE), back-scattered electrons (BSE) or mixed (SE+BSE) signal visions are gathered and photographed.

In the regions which include that structure, the particles are mostly arranged homogeneous, the shapes of them are cornered and fractured and the dimensions are in micrometers. The distances between these particles are seen to be narrowed. The dimensions are around 0.35-0.91 μm . In addition, spherical and closed spacing particles are seen along with geometrical shaped particles.

Another property which is seen in the SEM photographs is that the particles which have different sizes and shapes, have similar color tones. Although some particles are dark grey in color, in some regions light grey and white particles are also seen. That situation is obvious in all successive analysis. That image which is seen in the SEM photographs is a typical

crystalline structural shape which is also defined in literature. A homogenous structure is observed, the particles are observed to be in a tight form, large cavities and large particles are not observed.

In addition, nonstandard qualitative elemental analysis (SEM-EDS) is made on the inspected sample with X-ray mapping. (Figure 12 and Figure 13).

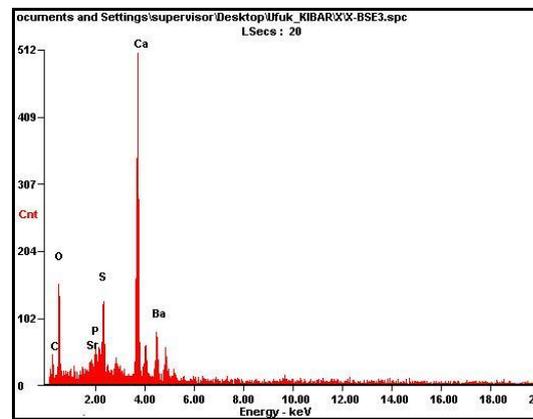
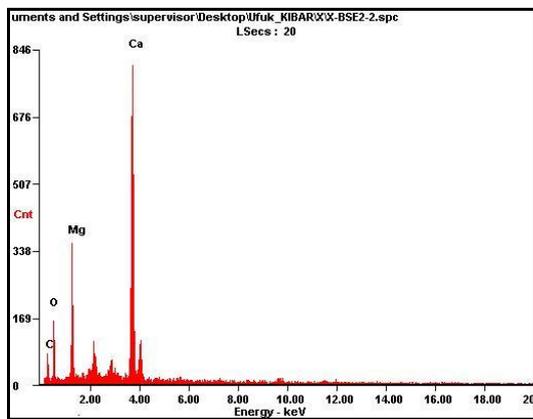


Fig 12 EDS Analysis Graphic

Fig 13 EDS Analysis Graphic

EDS analysis were applied by focusing on a point of 2 μm and it is applied by searching an area of (50 μm x 50 μm). That procedure is applied in a depth of 2.5 μm . In that analysis, the pure structure of the experiment sample is observed. In Table 3 and Table 4, atomic percentages which were obtained from EDS analysis are given.

Table 3 EDS atomic percentages

Elements	Atomic Percentage
C	29.86
O	40.37
Mg	12.80
Ca	16.96
Total	100.00

Table 4 EDS and atomic percentages

Elements	Atomic Percentage
C	24.47
O	52.27
Sr	0.67
P	1.73
S	4.08
Ca	14.00
Ba	2.79
Total	100.00

Moreover, EDS analysis indicate that various dissolutions were not formed, thus mainly a pure structure is observed during the analysis.

4.2. X-ray Diffraction (XRD Analysis) Findings

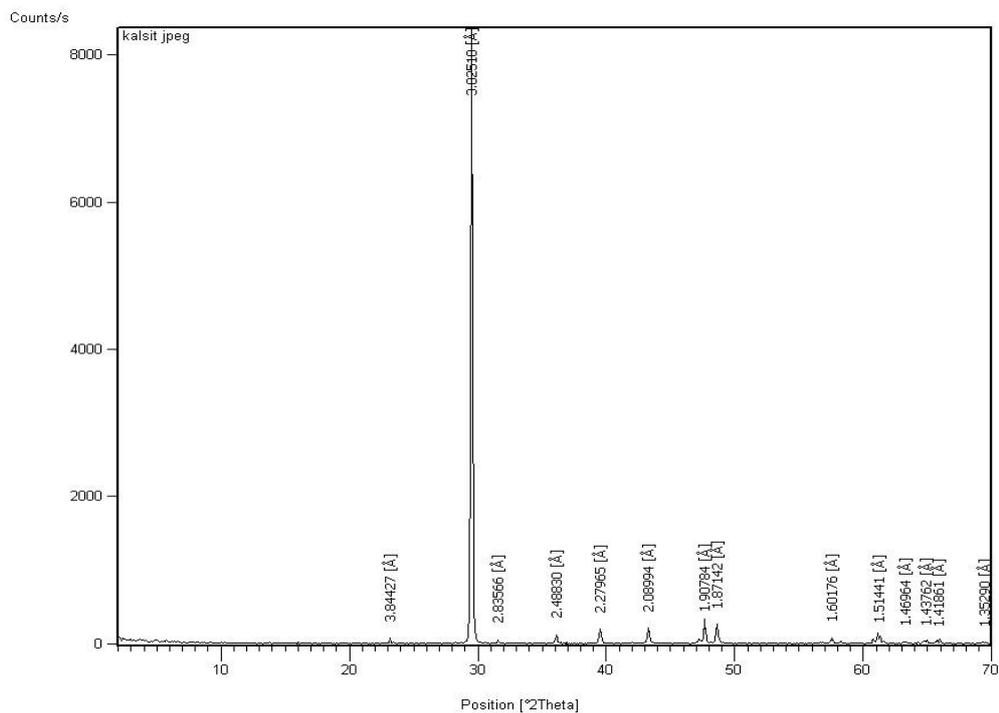


Fig 14.XRD Analysis Graphic

According to the results of XRD analysis in the Figure 14, the exterior and interior of main body of Naos are composed of calcite mineral.

While defining the microstructure of the experiment sample and while examining the crystal structure, X-ray analysis provided important findings. In the process, applying sintering with heat, the experiment samples are monitored from the nucleation phase to the last crystallization phase for crystallization duration and structural changes with XRD. These analysis have lots of benefits for observing different crystalline structures and for defining the appropriate heating conditions as well. Because of the same reason, the similarity between peak points indicates that the structure, which constitutes the sample, is in a pure phase, meaning that it is mainly composed of calcite mineral.

That situation is observed clearly in SEM photographs and it is compatible with XRD results.

5. RESULTS AND SUGGESTIONS

According to the data obtained from Turkish State Meteorological Service, the average temperature in Ankara is, lowest; $-21.5\text{ }^{\circ}\text{C}$ and highest; $+41.0\text{ }^{\circ}\text{C}$. Average of monly total rate amount is 51.2 kg/m^2 (Table 1). In addition, the daily total maximum rain amount is 88.9 kg/m^2 on 11.06.1997. Daily fastest wind is 115.6 km/hr on 12.01.1968. Daily highest snow amount is 30.0 cm in 05.01.2002 (Table 2). Therefore, the walls of Naos are under these climatic parameters (wind, heat, precipitation, freeze) for hundreds of years. That condition leads to freeze and thaw in patina layer and that causes spilling in the surface. Moreover; wind, temperature differences and rains accelerate the breaking of pieces from patina layer. The construction materials and construction chemicals which will be used for restoration of that historical temple have to be chosen with respect to the climatic parameters of Ankara.

Turkish Republic Ministry of Energy and Natural Resources, MTA Mineralogy and Petrography Analysis Laboratory Unit has made Scanning Electron Microscope (SEM) and EDS (Figure 11,12,13), X-ray Diffraction (XRD) analysis (Figure 14) . With respect to the analysis, the main component of the temple is determined to be stone with calcite mineral. According to that determination, the materials and chemicals which will be used in the restoration process, have to have calcite mineral origins or they have to be compatible with calcite mineral.

The pool with fountain (Figure 6), on the south side of the historical temple, is increasing the moisture rate and it is accelerating the deterioration of the Greek manuscript on the suth side wall of the temple. The original copy of manuscript was in Rome and it was destructed centuries ago. Therefore it is very important to keep the only remaining copy. The information given in the manuscript do not only belong to Roman Emperor Augustus, but also include important information about Roman history. Therefore, rather than a fountain, a classical hydrophore (pressurized recirculation pump) where the water is pouring step by step can be used. A pool system where the water is recirculating by machines can be considered.

A solution for roofing, which is compatible with the roofing system in the original building (Figure 2), can preserve the structure against climatic parameters and it can provide sustainability for the static equilibrium of the building. Such a precaution has to be taken urgently.

The temple whose importance for world heritage is unquestionable, has to be restored faithful to its originality. Environmental formation of the temple has to be in accordance with the surrounding structures. The historical structure has to be accessible to humanity as a museum, thus the honor, it deserves in the history, will be given back to it.

REFERENCES

1. Yurttagül, E., ‘‘Augustus Tapınađı Sondaj, Kurtarma Kazısı, Çevre Düzenlemesi ve Temizlik Çalışmaları’’, T.C. Ankara Valiliđi İl Kültür ve Turizm Müdürlüğü Anadolu Medeniyetleri Müzesi Müdürlüğü, Ankara, (2008).
2. M, Schede., D, Krencker., ‘‘*Der Tempel in Ankara*’’, pp. 43-44, Berlin - Leipzig, (1936).
3. Dođan, C, ‘‘Çevre Sorunlarının Tespitinde Ortaya Çıkan Kirliliklerin Mahalli İdarelerce Temizlenmesi; İlgili Hareket Alanını Belirleyen Normatif Pozitif Hukuk Kuralları’’, Askerî Yüksek İdâre Mahkemesi Dergisi, Sayı:19, s. 211, Ankara, (2004).
4. Aslan, İ., Güler, Ç., Yumak, E., ‘‘Ankara Augustus ve Roma Mabedi Fotoğraf Albümü’’, Ankara, (2013).
5. Özen, L., Zararsız, A., ‘‘Anadolu Medeniyetleri Müzesi Konservasyon Laboratuvarı Araştırma Çalışmaları’’, T.C. Ankara Valiliđi İl Kültür ve Turizm Müdürlüğü Anadolu Medeniyetleri Müzesi Müdürlüğü 2007-2008 Yıllığı, Ayrı Basım Sayı: XXI, S:309 Ankara, (2009).
6. Kadiođlu, S., Kadiođlu, K., Y., Akyol, A., A., ‘‘Augustus Tapınađı Arkeometrik İncelemeleri Kapsamında Jeofizik Çalışmalar’’, T.C. Kültür ve Turizm Bakanlığı Kültür Varlıkları ve Müzeler Genel Müdürlüğü 31. Uluslararası Kazı, Araştırma ve Arkeometri Sempozyumu, 25. Arkeometri Sonuçları Toplantısı, T.C. Kültür ve Turizm Bakanlığı Yayın No: 3251 / Kültür Varlıkları ve Müzeler Genel Müdürlüğü Yayın No: 144, s. 431-440, Denizli, Türkiye, 25-29 Mayıs (2009).
7. Sirt, E., ‘‘ Evaluation of biodeterioration in Nemrut Mount Monument and Temple of Augustus by using various techniques’’, METU, Ankara, (2011).
8. Botteri, P., Fangi G., ‘‘The Ancyra Project: the Temple of Augustus and Rome in Ankara -UNESCO 30th Anniversary Virtual Congress’’, 21-23, October, Alexandria, (2002).
9. Wallace, R., (Ed.) ‘‘Res gestae divi Augusti: as recorded in the **Monumentum Ancyranum** and the **Monumentum antiochenum**: introduction, grammatical notes, historical commentary, facing vocabulary’’, Wauconda, Ill, Bolchazy-Carducci Publishers, (2000).
10. Caner, E., N., Böke, H., ‘‘Occurrence of Calcium Oxalates on Marble Monuments in Anatolia’’, Proceedings of International Symposium on : The Oxalate Films: Origin and Significance in the Conservation of Works of Art, G. Alessandrini Ed., Centro CNR ‘‘GINO BOZZA’’ pp.299-307; Milano, (1989).
11. Caner, E., N., Göktürk, H., Türkmenođlu, A., G., Eseller, G., ‘‘Effects of Air Pollution on the Monuments in Ankara, Case Study: Temple of Augustus’’, Durability of Building Materials, 5, pp:463-473, (1989a).
12. Maden Tetkik Arama Genel Müdürlüğü, Petrografi Laboratuvarı, Ankara, (2013).
13. http://www.mgm.gov.tr/App Themes/mavimavi/site_baslik_v1_tr.png, (2013).